

Study on the Oxide Formation for Alloy 800 at pH 8.4

Chong-Hun Jung*

Decommissioning Technology Research Division, Korea Atomic Energy Research Institute

**Corresponding author: E-mail: nchjung@kaeri.re.kr*

Abstract: As a material with high corrosion resistance and mechanical strength, Incoloy Alloy 800 has been widely used as a structural material for devices and equipment requiring corrosion and heat resistance, strength and stability at high temperatures up to about 800C. Because of these properties, it has been effectively used in piping systems or heat exchangers using nitric acid media, which require resistance to chlorine SCC, and is often used as a steam generator tube in nuclear power plants. Therefore, as part of the experiment to suppress the corrosion of Alloy 800, which has a large use, the effect of potential on oxide formation and conversion on alloy 800 under potentiodynamic conditions at pH 8.4 was investigated.

Keywords: Oxide formation, Incoloy 800, Cyclic voltammetry(CV)

1. Introduction

The steam generator is a major facility that can cause various safety problems, especially problems related to corrosion and mechanical damage, during operation connecting the primary and secondary systems. As a driving factor that can deteriorate the steam generator of a CANDU nuclear power plant, water chemistry is very important because corrosion of structural materials is closely related to water chemistry conditions. A number of studies have been conducted on the corrosion of structural materials of steam generators at CANDU nuclear power plants. Much research on the formation of corrosion oxides caused by changes in factors related to water chemistry or electrochemistry (potential, temperature, pH, etc.) to suppress corrosion of materials such as carbon steel, SS316L, Co-based Alloy (Stellite-6), which have high mechanical strength and high corrosion resistance has been performed [1-4]. INCOLOY alloy 800 is a widely used material for construction of equipment requiring corrosion resistance, heat resistance up 1500F, and mechanical strength. In chemical and petrochemical processing, the alloy is used for heat exchangers and piping systems in nitric acid media. In nuclear power plants, it is used for steam generator tubing in pressurized water reactors (PWRs), including Canadian Deuterium Uranium (CANDU®) reactors. However, failures resulting from localized corrosion such as pitting, crevice and stress corrosion cracking (SCC) have been observed in the service environments. There exists still considerable controversy over the type of oxide that can be formed and the mechanism of oxide formation on Alloy 800.

The objectives of this study are to investigate the effect of potential on oxide formation and conversion on alloy 800 under potentiodynamic conditions at pH 8.4.

2. Experimental

The studied material in this work was Alloy 800 containing 43 wt% Fe, 33 wt% Ni and 22 wt% Cr, as shown in Table 1. Electrodes prepared from the metals had a flat, circular face, with a surface area of 0.7 cm². Prior to each experiment the sample surface was abraded manually with 400, 600, and then 1200 grit SiC papers, polished with 1 μm MetaDi Supreme diamond paste suspension (Buehler) on Texmet microcloth (Buehler), and then finally sonicated in an acetone/methanol mixture for 5 min to remove surface residues. All experiments were conducted at room temperature in Ar-sparged 0.01 M sodium borate solutions. The de-aerated solutions were prepared using reagent grade Na₂B₄O₇. A pH of 8.4 was obtained by adding appropriate amounts of 1 M boric acid solution to the borate solution.

A Solartron model 1480 multistat was used in all electrochemical measurements. Before each experiment the electrolyte solution was Ar-purged for at least 60 min. The freshly prepared working electrode was then cathodically cleaned at "1.1 V_{SCE} for 5 min. For tests performed under each set of temperature conditions, a series of electrochemical tests on cyclic voltammetry at different vertex potentials with the scan rate of 0.17 mV/s was performed.

Table 1. Chemical Compositions for INCOLOY alloys 800 (%).

Nickel	30.0-35.0
Chromium	19.0-23.0
Iron	39.5 min.
Carbon	0.10 max.
Aluminum	0.15-0.60
Titanium	0.15-0.60
Aluminum +0Titanium	0.30-1.20
ASTM grain size	Not specified

3. Results and Discussion

Figure 1-4 show the CV results at room temperature at three different vertex potentials i.e -0.2, 0.0 and 0.4 V_{SCE}. In the CV results, there are some peaks labeled as A1, A2 and A3 for anodic peaks and C1 for the cathodic peak. These peaks show the transformation of one type of oxide to the other one.

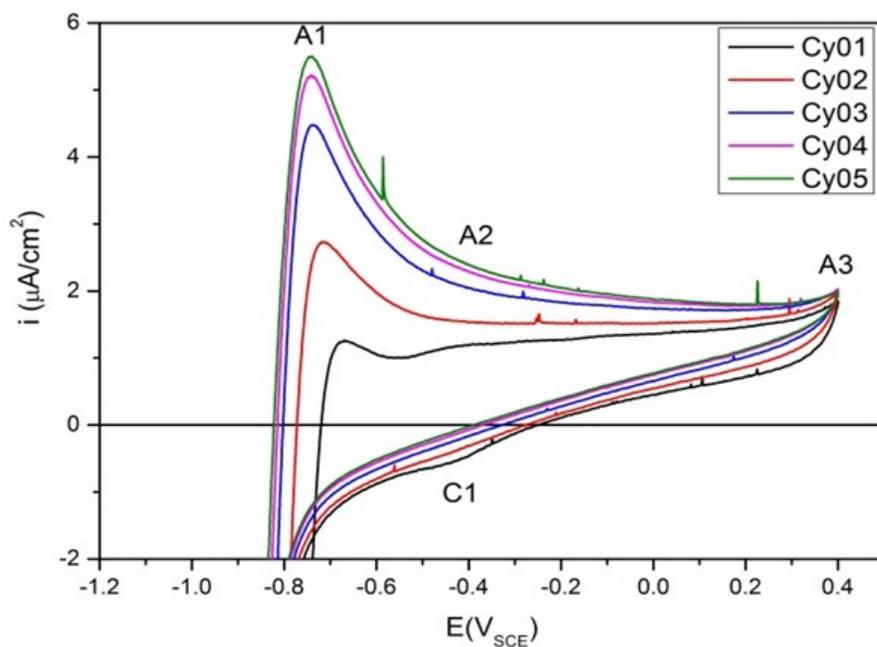


Fig. 1. Cyclic Voltammetry (CV) results on the Alloy 800 at room temperature in 0.01 M borate buffer solution with $\text{pH}_{25^\circ\text{C}}=8.4$ and potential $0.4 \text{ V}_{\text{SCE}}$.

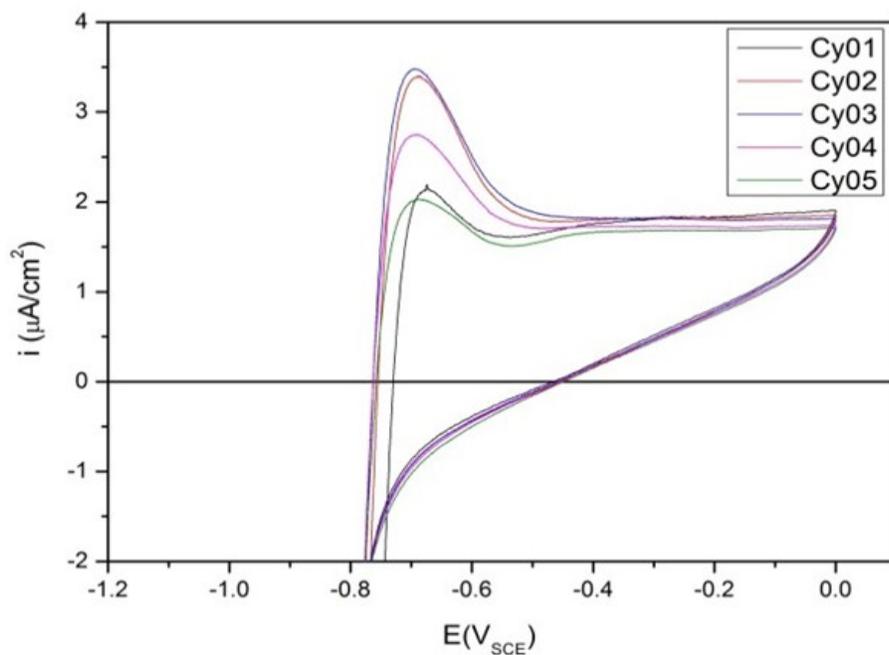


Fig. 2. Cyclic Voltammetry (CV) results on the Alloy 800 at room temperature in 0.01 M borate buffer solution with $\text{pH}_{25^\circ\text{C}}=8.4$ and potential $0.0 \text{ V}_{\text{SCE}}$.

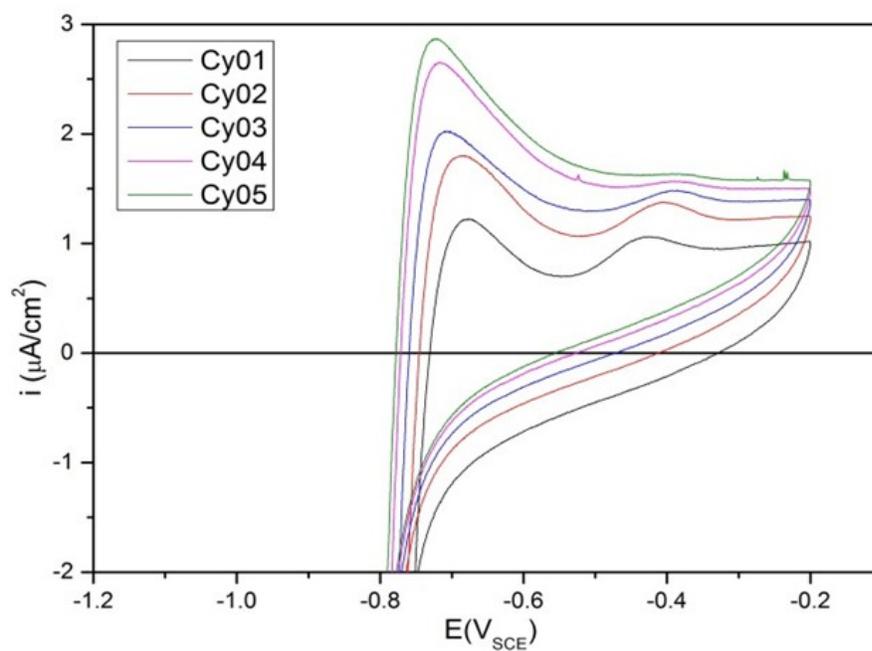


Fig. 3. Cyclic Voltammetry (CV) results on the Alloy 800 at room temperature in 0.01 M borate buffer solution with $\text{pH}_{25^{\circ}\text{C}}=8.4$ and potential $-0.2 \text{ V}_{\text{SCE}}$.

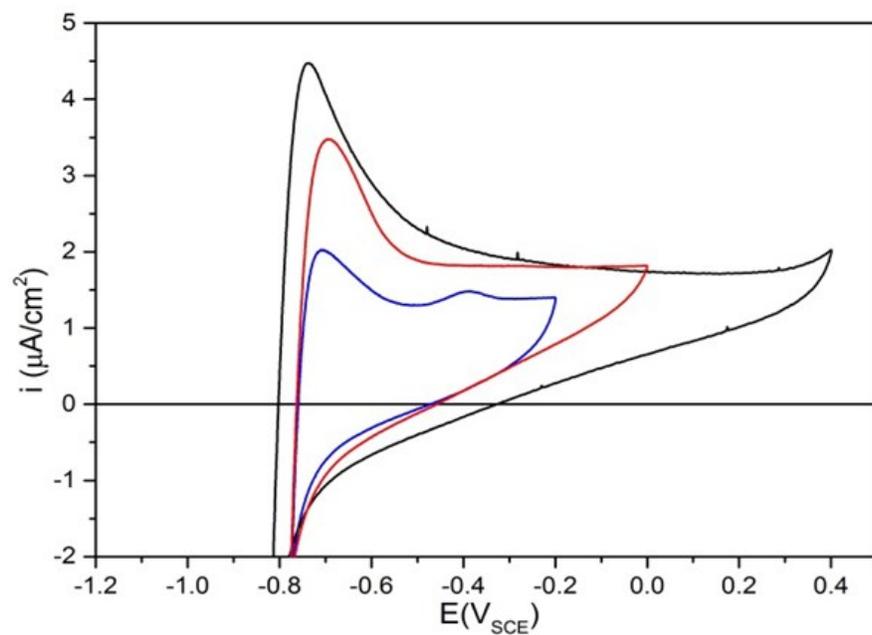


Fig. 4. Comparison of the third cycle of cyclic voltammetry (CV) at room temperature and different vertex potentials.

Peak A1

In the range of potential of peak A1, anodic oxidation of Fe to Fe²⁺ oxide like FeO, Fe(OH)₂ or FeCr₂O₄ and Fe to Fe^{2+/3+} oxide i.e. Fe₃O₄ is all possible from thermodynamic point of view. For all three vertex potentials, the intensity of peak increase by cycles and the potential shifts to more negative values. It shows that number of reactive sites increases by number of cycles and the shift to more negative potentials might be an indication of more feasible formation of iron chromate. It can be said that surface is covered by a two types of oxide after peak A1, an inner layer of iron chromate and outer layer of magnetite. Both of these oxides are known to have a spinal structure, highly insoluble and hard to reduce. This is why there is no corresponding cathodic peak for peak A1. The cathodic at very negative potentials is due to water reduction.

Oxidation of Cr to Cr³⁺ and hydrated Fe²⁺ hydroxide to α -FeOOH is also thermodynamically possible in the potential range of peak A1, however, both of these reactions are kinetically slow. Oxidation of Cr to Cr³⁺ requires the movement of chromium cations and oxygen anions through the pre-existed air-formed oxide and also chromate and magnetite layer on the surface which produces a very large energy barrier for this reaction. Conversion of hydrated Fe²⁺ hydroxide to α -FeOOH is likely impossible because it needs significant change in oxide structure. In addition to all of above reasons, the paths for formation of magnetite and chromite are facile and their formation is more likely from kinetic point of view.

Peak A2 and peak C1

Another peaks appear at potential range of -0.45 V_{SCE} and in backward scan a cathodic peak at the same potential. Although the intensity of the peak does not change significantly, due to other peaks current intensity and background current density, this peak is more obvious when the upper limit of scan is below 0.0 V_{SCE}. In addition, the intensity of this peak is diminished by increase in number of cycles which shows lower reactive sites for this reaction is possible at higher cycles. Previous studies showed that this peak for both carbon steel and SS316 is due to conversion of Fe₃O₄ to α -Fe₂O₃ [5-6] and here the same reaction is considered. Magnetite and Maghemite have nearly close crystalline structure and this makes their conversion to occur easily.

Considering high amount of nickel in this alloy (~33 wt%), it can be seen that in addition to the iron oxides conversion, oxidation of Ni to Ni²⁺ in the form of NiO/ Ni(OH)₂ and NiFe₂O₄ is also possible. As a result, this peak can be also attributed to the oxidation of nickel.

Peak A3

When the scan limit is beyond 0.2 V_{SCE}, at potentials just below 0.4 V_{SCE} the current density starts to increase. By looking to the thermodynamic potentials, this increase in current is due to the oxidation of Cr³⁺ to Cr⁶⁺. Mechanism for this oxidation is presented previously [6], here in short, since oxidation of magnetite to α -FeOOH is also possible

from thermodynamic point of view and the fact that it is known that this oxidation causes fracture in oxide, it exposes the inner Cr^{3+} oxide to the solution and its oxidation to highly Cr^{6+} oxide occurs and leads to an increase in current density.

Figure 5-8 shows CV results at 80 °C for different vertex potentials. The result at this temperature is very similar to those of room temperature except for vertex potential of $0.4 \text{ V}_{\text{SCE}}$ which shows another anodic peak A3 at $0.0 \text{ V}_{\text{SCE}}$ and a cathodic peak at potential around $-0.2 \text{ V}_{\text{SCE}}$. These anodic and cathodic peaks are attributed to the conversion of magnetite to $\alpha\text{-FeOOH}$ as it is previously reported [2]. As can be seen, in this temperature, only peak A1 can be seen and high dissolution of iron and nickel avoids appearance of other peaks. However, for the CV results with vertex potential of $0.0 \text{ V}_{\text{SCE}}$, peaks A2/C2 can be seen as broad low current intensity peaks. Same discussion on the results of this temperature can be done as it was for the room temperature except for higher dissolution rate at 80 °C.

Similar potential regions as room temperature can be defined here. Based on these results, corrosion potential of Alloy 800 at this temperature and pH locates at region 2 in which the surface is covered by an inner iron chromate layer and outer layer of Ni^{2+} oxide.

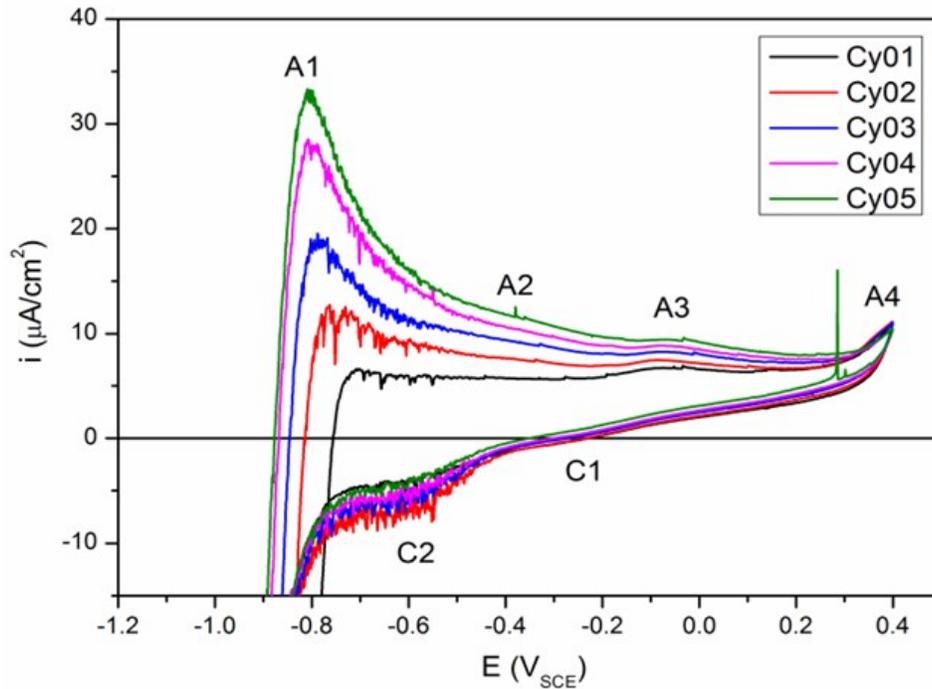


Fig. 5. Cyclic Voltammetry (CV) results on the Alloy 800 at 80 °C in 0.01 M borate buffer solution with $\text{pH}_{25^\circ\text{C}}=8.4$ and potential $0.4 \text{ V}_{\text{SCE}}$.

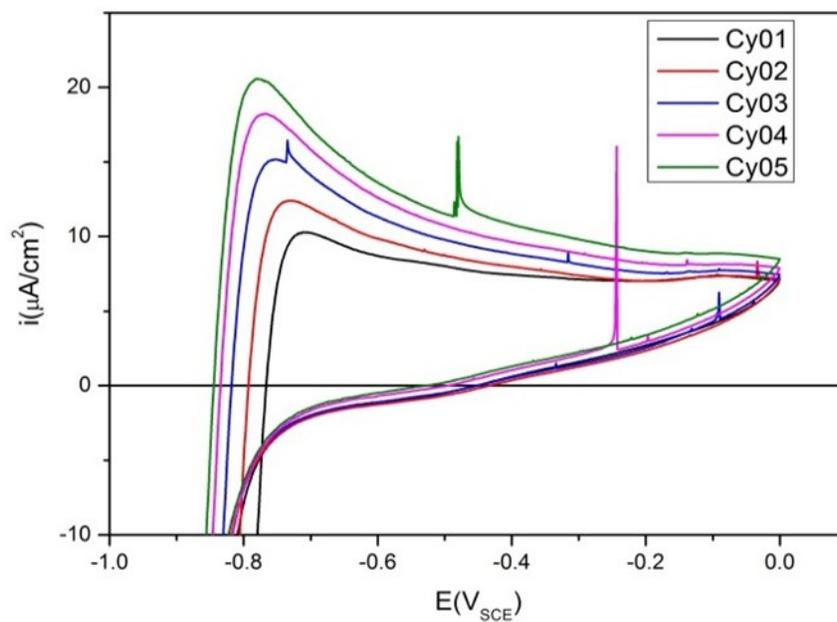


Fig. 6. Cyclic Voltammetry (CV) results on the Alloy 800 at 80 °C in 0.01 M borate buffer solution with $\text{pH}_{25^\circ\text{C}}=8.4$ and potential $0.0 \text{ V}_{\text{SCE}}$.

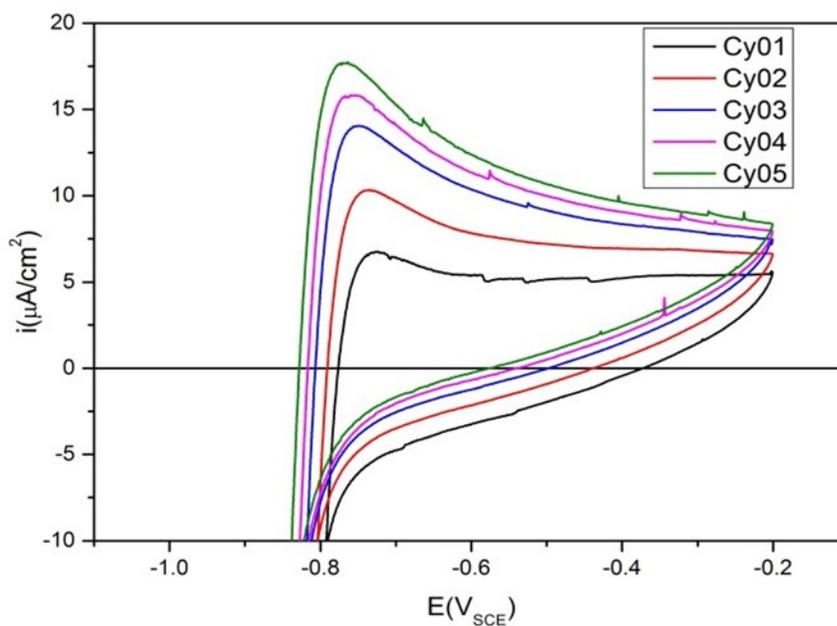


Fig. 7. Cyclic Voltammetry (CV) results on the Alloy 800 at 80 °C in 0.01 M borate buffer solution with $\text{pH}_{25^\circ\text{C}}=8.4$ and potential $-0.2 \text{ V}_{\text{SCE}}$.

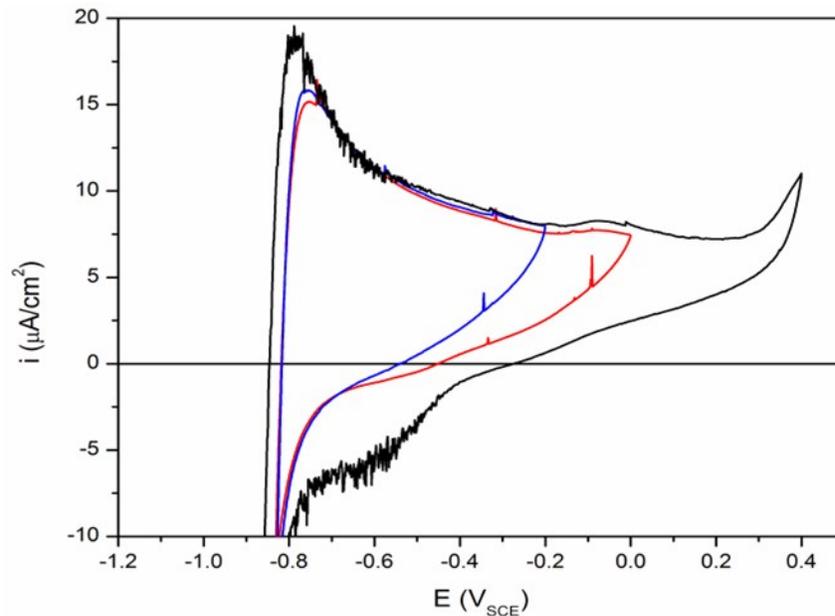


Fig. 8. Comparison of the third cycle of cyclic voltammetry (CV) at 80 °C and different vertex potentials

4. Conclusions

The Based on this discussion, potential regions in CV results can be summarized as follow:

Region I ($E < -0.5 V_{SCE}$): in this potential range, oxidation of Fe is limited to formation of $Fe^{2+}/^{3+}$ oxides. The initial air-formed chromium oxide which is defective is converted to chromite as an inner oxide layer and there will be a magnetite oxide as an outer oxide layer.

Region II ($-0.5 V_{SCE} < E < 0.0 V_{SCE}$): in this potential range, oxidation of $Fe^{2+}/^{3+}$ to Fe^{3+} is possible and also the conversion of the initial pre-existed oxide to chromite is completed.

Region III ($0.0 V_{SCE} < E < 0.3 V_{SCE}$): At potential above $0.0 V_{SCE}$, oxidation of Fe_3O_4 to α - $FeOOH$ is possible and causes some fractures in the oxide. These fractures in the presence of aggressive halides can lead to the localized corrosion like pitting and crevice corrosion.

Region IV ($E > 0.3 V_{SCE}$): In this region, oxidation of Cr^{3+} oxide to Cr^{6+} occurs and since Cr^{6+} is highly soluble, current density increases.

By looking to the CV and corrosion potential measurement results, corrosion potential in this pH and room temperature locates at the region one, i.e. the surface is covered by an inner iron chromate oxide and an outer magnetite. Same discussion on the results of this temperature can be done as it was for the room temperature except for higher dissolution rate at 80 °C. Based on these results, corrosion potential of Alloy 800 at this temperature and pH locates at region 2 in which the surface is covered by an inner iron chromate layer and outer layer of Ni^{2+} oxide.

Acknowledgement

The authors would like to express their appreciation to the National Research Foundation (NRF) of Korea for the award of a grant funded by the Ministry of Science and ICT (MIST) of the Republic of Korea, in support of the authors' work through the Nuclear Research and Development Program (NRF-2018M2B2B1065634).

References

- [1] J. Gui, T.M. Devine, *Corrosion Science* 32 (1991) 1105
- [2] J.C. Rubim, J. Dunnwald, *Journal of Electroanalytical Chemistry* 258 (1989) 327.
- [3] M. Kerkar, J. Robinson, A.J. Forty, *Faraday Discussions* 89 (1990) 31.
- [4] M.P. Ryan, R.C. Newman, G.E. Thompson, *Journal of the Electrochemical Society* 142 (1995) L177.
- [5] W. Xu, K. Daub, X. Zhang, J.J. Noel, D.W. Shoesmith, J.C. Wren, *Electrochimica Acta* 54 (2009) 5727.
- [6] Q.W. Knapp, J.C. Wren, *Electrochimica Acta* 80 (2012) 90. Faure S "Innovative Processes for nuclear decontamination solids" Exchange meeting between KAERI-CEA (2008).



This document was created with the Win2PDF "print to PDF" printer available at <http://www.win2pdf.com>

This version of Win2PDF 10 is for evaluation and non-commercial use only.

This page will not be added after purchasing Win2PDF.

<http://www.win2pdf.com/purchase/>